

Glass in building — Heat soaked thermally toughened soda lime silicate safety glass —

Part 1: Definition and description

The European Standard EN 14179-1:2005 has the status of a
British Standard

ICS 81.040.20

National foreword

This British Standard is the official English language version of EN 14179-1:2005.

The UK participation in its preparation was entrusted by Technical Committee B/520, Glass and glazing in building, to Subcommittee B/520/1, Glass and glazing in building — Basic and transformed glass products, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 43 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 11 July 2005

© BSI 11 July 2005

ISBN 0 580 46362 1

ICS 81.040.20

English version

Glass in building - Heat soaked thermally toughened soda lime silicate safety glass - Part 1: Definition and description

Verre dans la construction - Verre de silicate sodocalcique de sécurité trempé et traité Heat Soak - Partie 1: Définition et description

Glas im Bauwesen - Heißgelagertes thermisch vorgespanntes Kalknatron-Einscheibensicherheitsglas - Teil 1: Definition und Beschreibung

This European Standard was approved by CEN on 19 May 2005.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents	Page
Foreword	4
Introduction.....	5
1 Scope	6
2 Normative references	6
3 Terms and definitions.....	6
4 Glass products.....	7
5 Manufacturing processes.....	7
5.1 General	7
5.2 Toughening process.....	7
5.3 Heat soak process cycle	8
6 Heat soak process system	9
6.1 General	9
6.2 Oven.....	9
6.3 Glass support.....	9
6.4 Glass separation	9
6.5 Calibration	11
7 Fracture characteristics	11
8 Dimensions and tolerances.....	11
8.1 Nominal thickness and thickness tolerances	11
8.2 Width and length (sizes).....	12
8.3 Flatness	14
9 Edge work, holes, notches and cut-outs.....	17
9.1 Warning	17
9.2 Edge working of glass for toughening	17
9.3 Profiled edges	18
9.4 Round holes	18
9.5 Notches and cut-outs	21
9.6 Shaped panes.....	21
10 Fragmentation test.....	22
10.1 General	22
10.2 Dimensions and number of test specimens	22
10.3 Test procedure	22
10.4 Assessment of fragmentation	23
10.5 Minimum values from the particle count.....	24
10.6 Selection of the longest particle	24
10.7 Maximum length of longest particle	24
11 Other physical characteristics	24
11.1 Optical distortion	24
11.2 Anisotropy (iridescence)	24
11.3 Thermal durability	25
11.4 Mechanical strength	25
11.5 Classification of performance under accidental human impact.....	25
12 Marking	25
Annex A (normative) Heat soak process system calibration test	26
A.1 Calibration criteria	26

A.2	Loading of oven and position for glass surface temperature measurement	26
A.3	Procedure	27
A.4	Records	27
A.5	Interpretation of the calibration test	28
Annex B (informative)	Curved heat soaked thermally toughened soda lime silicate safety glass	37
Annex C (informative)	Examples of particle count	38

Foreword

This European Standard (EN 14179-1:2005) has been prepared by Technical Committee CEN/TC 129 "Glass in building", the secretariat of which is held by IBN/BIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2005, and conflicting national standards shall be withdrawn at the latest by December 2005.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

This Part of the European Standard does not stand-alone, it is a part of one standard:

- EN 14179-1: Glass in building – Heat soaked thermally toughened soda lime silicate safety glass – Part 1: Definition and description;
- EN 14179-2: Glass in building – Heat soaked thermally toughened soda lime silicate safety glass – Part 2: Evaluation of conformity/Product standard.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Introduction

Heat soaked thermally toughened soda lime silicate safety glass has a safer breakage behaviour when compared with annealed glass. It also has a known level of residual risk of spontaneous breakage arising from the possible presence of critical nickel sulphide (NiS) inclusions in the thermally toughened soda lime silicate glass.

NOTE 1 This case deals with extremely large quantities of glass. These quantities are dealt with on a statistical basis. Therefore it is impossible to select a quantity of heat soaked thermally toughened soda lime silicate safety glass, for a building, and claim that 'no break' by NiS inclusion can occur. The breakage of heat soaked thermally toughened soda lime silicate safety glass caused by other influences is excluded.[s1]

When used to offer protection under accidental human impact, heat soaked thermally toughened soda lime silicate safety glass also should be classified according to EN 12600 (all parts).

NOTE 2 CEN/TC 129/WG 8 is producing standards for the determination of the design strength of glass and is preparing a design method.

The European Committee for Standardization (CEN) draws attention to the fact that it is claimed that compliance with this document may involve the use of a patent concerning Heat Soak Tests. CEN takes no position concerning the evidence, validity and scope of this patent right. The holder of this patent right has assured CEN that he/she is willing to negotiate licences under reasonable and non-discriminatory terms and conditions with applicants throughout the world. In this respect, the statement of the holder of this patent right is registered with CEN. Information may be obtained from:

SAINT-GOBAIN GLASS FRANCE

Les Miroirs – 92096 La Défense Cedex

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights other than those identified above. CEN shall not be held responsible for identifying any or all such patent rights.

1 Scope

This European Standard specifies the heat soak process system together with tolerances flatness, edgework, fragmentation and physical and mechanical characteristics of monolithic flat heat soaked thermally toughened soda lime silicate safety glass for use in buildings.

Information on curved heat soak thermally toughened soda lime silicate safety glass is given in Annex B, but this product does not form part of this European Standard.

Other requirements, not specified in this European Standard, can apply to heat soaked thermally toughened soda lime silicate safety glass which is incorporated into assemblies, e.g. laminated glass or insulating units, or undergo an additional treatment, e.g. coating. The additional requirements are specified in the appropriate product standard. Heat soak thermally toughened soda lime silicate safety glass, in this case, does not lose its mechanical or thermal characteristics.

2 Normative references

The following referenced documents are indispensable for the application of this European Standard. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 572-1, *Glass in building — Basic soda lime silicate glass products — Part 1: Definitions and general physical and mechanical properties*

EN 572-2, *Glass in building — Basic soda lime silicate glass products — Part 2: Float glass*

EN 572-4, *Glass in building — Basic soda lime silicate glass products — Part 4: Drawn sheet glass*

EN 572-5, *Glass in building — Basic soda lime silicate glass products — Part 5: Patterned glass*

EN 1096-1, *Glass in building — Coated glass — Part 1: Definitions and classification*

3 Terms and definitions

For the purposes of this European Standard, the following terms and definitions apply.

3.1

heat soaked thermally toughened soda lime silicate safety glass

glass within which a permanent surface compressive stress has been induced in order to give it greatly increased resistance to mechanical and thermal stress and prescribed fragmentation characteristics and which has a known level of residual risk of spontaneous breakage due to the presence of critical nickel sulphide (NiS) inclusions

3.2

level of residual risk

risk of spontaneous breakage of heat soaked thermally toughened soda lime silicate safety glass, on a statistical basis, due to the presence of critical nickel sulphide inclusions, is no more than one breakage per 400 tonnes of heat soaked thermally toughened soda lime silicate safety glass

3.3

flat heat soaked thermally toughened soda lime silicate safety glass

heat soaked thermally toughened soda lime silicate safety glass that has not been deliberately given a specific profile during manufacture

3.4

heat soaked enamelled thermally toughened soda lime silicate safety glass

heat soaked thermally toughened soda lime silicate safety glass which has a ceramic frit fired into the surface during the toughening process. After toughening the ceramic frit becomes an integral part of the glass

NOTE In the UK, this glass is also known as heat soaked opaque thermally toughened soda lime silicate safety glass.

3.5

horizontal toughening

process in which the glass is supported on horizontal rollers

3.6

vertical toughening

process in which the glass is suspended by tongs

4 Glass products

Heat soaked thermally toughened soda lime silicate safety glass shall be made from a monolithic soda lime silicate glass product generally corresponding to one of the following standards:

- soda lime silicate glass according to EN 572-1;
- float glass according to EN 572-2;
- drawn sheet glass according to EN 572-4;
- patterned glass according to EN 572-5;
- coated glass according to EN 1096-1.

5 Manufacturing processes

5.1 General

Heat soaked thermally toughened soda lime silicate safety glass is manufactured as follows:

Basic soda lime silicate glass products (see Clause 4) are cut to size, shaped and edgeworked (see Clause 9).

The prepared glass panes are then thermally toughened (see 5.2).

The thermally toughened panes are then subjected to the heat soak process cycle.

After manufacture the heat soaked thermally toughened soda lime silicate glass shall comply with the fragmentation test (see Clause 10) and mechanical strength requirement (see 11.4).

5.2 Toughening process


The cut, shaped and edgeworked glasses are toughened. The horizontal or vertical toughened glass shall comply with the flatness criteria (see 8.3).

The thermally toughened soda lime silicate glass shall have a level of fragmentation that will ensure that after the glass has been through the heat soak process, and subsequently tested to the fragmentation test (see Clause 10), it shall comply with 10.5.

5.3 Heat soak process cycle

5.3.1 General

The heat soak process cycle consists of a heating phase, a holding phase and a cooling phase (see Figure 1).

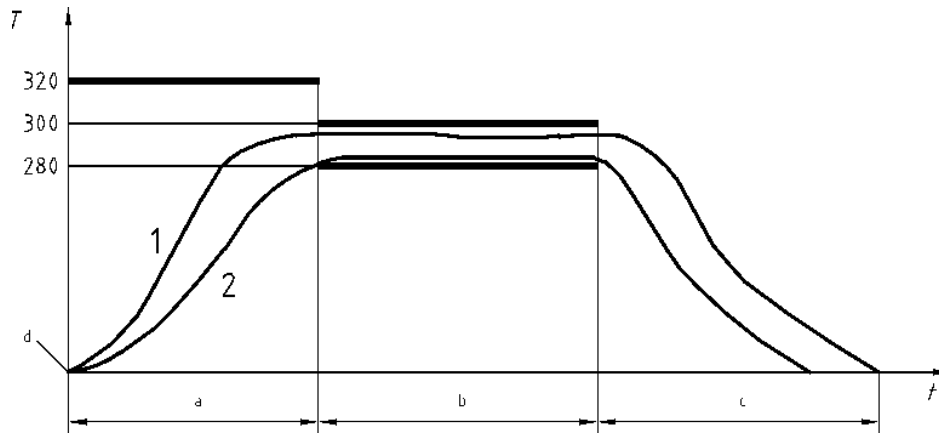

Key

- | | |
|--|-------------------------|
| T glass temperature at any point, °C | d ambient temperature |
| t time, h | a heating phase |
| 1 first glass to reach 280 °C | b holding phase |
| 2 last glass to reach 280 °C | c cooling phase |

Figure 1 — Heat soak process cycle

5.3.2 Heating phase

The heating phase commences with all the glasses at ambient temperature and concludes when the surface temperature of the last glass reaches 280 °C. The time to reach this temperature is defined in the calibration process. This time will be dependent on the size of the oven, the amount of glass to be treated, the separation between glasses and the heating system capacity.

NOTE 1 The glass separation and rate of heating should be controlled to minimise the risk of glass breakage as a result of thermal stress.

To facilitate economic heating, the air temperature within the oven may exceed 320 °C. However, the glass surface temperature shall not be allowed to exceed 320 °C. The period of glass surface temperature in excess of 300 °C shall be minimised.

NOTE 2 When the temperature of the glass exceeds 300 °C, care should be taken to ensure that the properties of the heat soaked thermally toughened soda lime silicate safety glass are not significantly altered i.e. they continue to meet Clause 10.

5.3.3 Holding phase

The holding phase commences when the surface temperature of all the glasses has reached a temperature of 280 °C. The duration of the holding phase is 2 h.

Precise oven control is necessary in order to ensure that the glass surface temperature shall be maintained in the range of 290 °C ± 10 °C during the holding phase.

5.3.4 Cooling phase

The cooling phase commences when the last glass to reach 280 °C has completed its holding phase, i.e. been held for two hours at 290 °C ± 10 °C. During this phase the glass temperature shall be brought down to ambient temperature.

The cooling phase can be concluded when the air temperature in the oven reaches 70 °C.

NOTE The rate of cooling should be controlled to minimise the risk of glass breakage as a result of thermal stress.

6 Heat soak process system

6.1 General

The heat soak process system consists of:

- oven (see 6.2);
- glass support (see 6.3);
- separation system (see 6.4).

The oven shall be calibrated, see 6.5 and Annex A, and this determines the method of operation of the heat soak process system during manufacture of heat soaked thermally toughened soda lime silicate safety glass.

6.2 Oven

The oven shall be heated by convection and shall allow an unhindered air circulation around each glass pane. In the event of glass breakage the airflow shall not be hindered. The airflow in the oven shall be led parallel to the glass surfaces.

NOTE The openings for the air ingress/egress should be designed to ensure that fragments of broken glass do not cause blockages.

6.3 Glass support

Glasses may be supported vertically or horizontally. The glasses shall not be fixed or clamped, they have to be supported to allow free movement.

NOTE Vertically means true vertical or up to 15° either side of true vertical.

The distance between glasses affects the airflow, heat exchange and the heating time. Glass to glass contact shall not be allowed.

6.4 Glass separation

The glasses shall be separated in a manner that does not hinder the airflow. The separators shall also not hinder the airflow e.g. see Figure 2.

Dimensions in millimetres

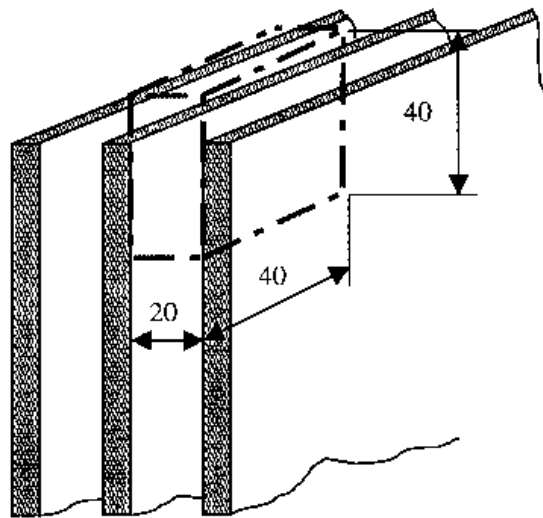


Figure 2 — Example of a vertical glass support

The minimum separation of the glasses shall be determined during the calibration of the oven, see 6.5 and Annex A.

NOTE 1 Generally, a minimum separation of 20 mm is recommended (see Figure 3).

NOTE 2 If glasses of very different size are put on the same stillage, they will require greater separation in order to prevent glass breakage when the furnace is opened after the heat soak process. The same applies to glasses with holes, notches and cut-outs.

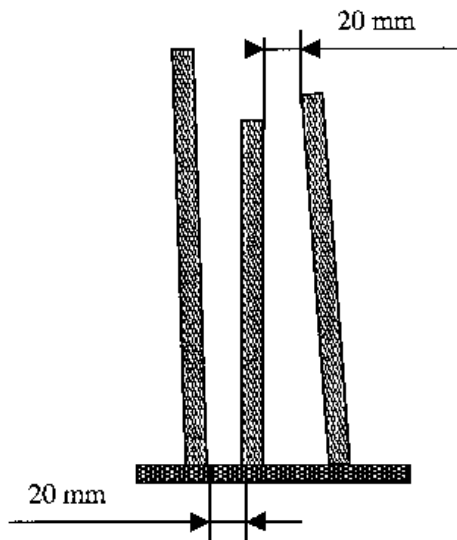


Figure 3 — Recommend separation between glass

The positioning of the separators, material of the manufacture and their shape shall be specified during the calibration test of the oven and shall be reproduced during the manufacturing process.

6.5 Calibration

The heat soak system, e.g. oven, glass separation, separators, etc., shall be calibrated, see Annex A.

The calibration shall determine the heating phase of the process, glass separation distance, the positioning, material and shape of separators, the type and positioning of stillage(s) and define the operating conditions for use during manufacture.

7 Fracture characteristics

In the event of breakage, heat soaked thermally toughened soda lime silicate safety glass fractures into numerous small pieces, the edges of which are generally blunt.

NOTE Fragmentation in service does not always correspond to that described in Clause 10, due to restraint from fixing or reprocessing (e.g. laminating), or due to the cause of fracture.

8 Dimensions and tolerances

8.1 Nominal thickness and thickness tolerances

The nominal thicknesses and thickness tolerances are those given in the relevant product standard (see Clause 4), some of which are reproduced in Table 1.

Table 1 — Nominal thicknesses and thickness tolerances

Dimensions in millimetres

Nominal thickness d	Thickness tolerances for glass type		
	Drawn sheet	Patterned	Float
3	±0,2	±0,5	±0,2
4	±0,2	±0,5	±0,2
5	±0,3	±0,5	±0,2
6	±0,3	±0,5	±0,2
8	±0,4	±0,8	±0,3
10	±0,5	±1,0	±0,3
12	±0,6	not manufactured	±0,3
15	not manufactured	not manufactured	±0,5
19	not manufactured	not manufactured	±1,0
25	not manufactured	not manufactured	±1,0

The thickness of a pane shall be determined as for the basic product. The measurement shall be taken at the centres of the 4 sides, and away from the area of any tong marks (see Figure 6), which may be present.

8.2 Width and length (sizes)

8.2.1 General

When heat soaked thermally toughened soda lime silicate safety glass dimensions are quoted for rectangular panes, the first dimension shall be the width, *B*, and the second dimension the length, *H*, as shown in Figure 4. It shall be made clear which dimension is the width, *B*, and which is the length, *H*, when related to its installed position.

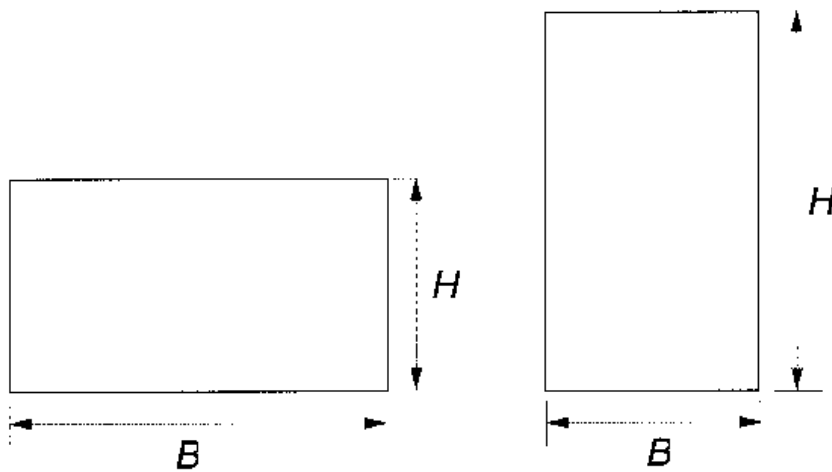


Figure 4 — Examples of width, *B*, and length, *H*, relative to the pane shape

NOTE For heat soaked thermally toughened soda lime silicate safety glass manufactured from patterned glass, the direction of the pattern should be specified relative to one of the dimensions.

8.2.2 Maximum and minimum sizes

For maximum and minimum sizes, the manufacturer shall be consulted.

8.2.3 Tolerances and squareness

The nominal dimensions for width and length being given, the finished pane shall not be larger than a prescribed rectangle resulting from the nominal dimensions increased by the tolerance, t , or smaller than a prescribed rectangle reduced by the tolerance, t . The sides of the prescribed rectangles are parallel to one another and these rectangles shall have a common centre (see Figure 5). The limits of squareness shall be determined by the prescribed rectangles. Tolerances are given in Table 2.

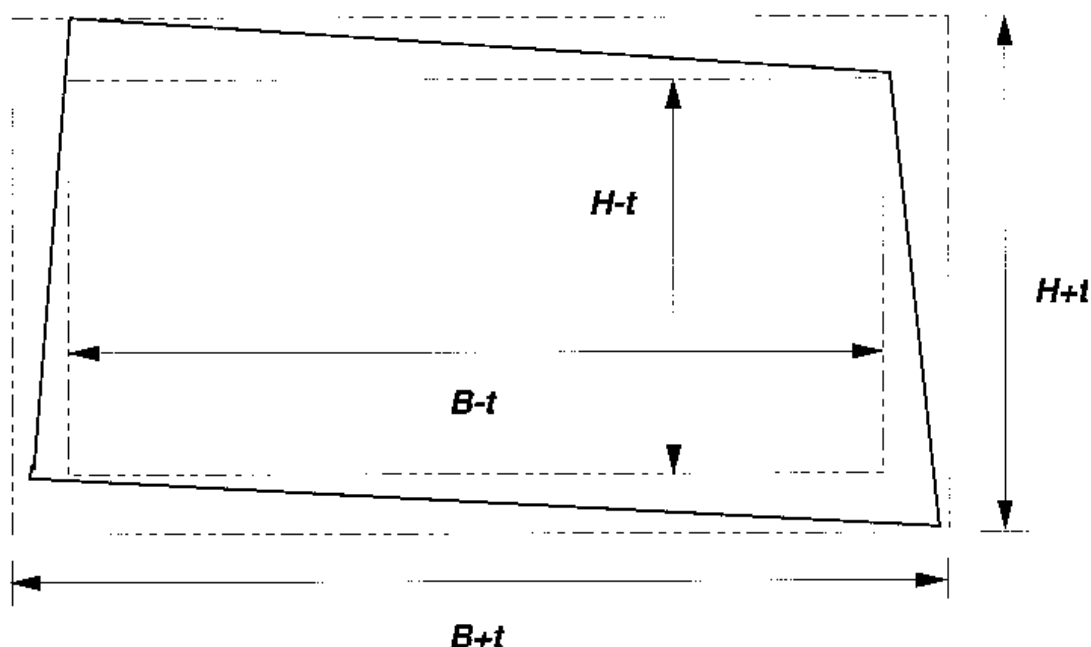


Figure 5 — Tolerance limits for dimensions of rectangular panes


Table 2 — Tolerances on width, B , and length, H

Dimensions in millimetres

Nominal dimension of side, B or H	Tolerance, t	
	nominal glass thickness, $d \leq 12$	nominal glass thickness, $d > 12$
$\leq 2\,000$	$\pm 2,5$ (horizontal toughening) $\pm 3,0$ (vertical toughening)	$\pm 3,0$
$2\,000 < B$ or $H \leq 3\,000$	$\pm 3,0$	$\pm 4,0$
$> 3\,000$	$\pm 4,0$	$\pm 5,0$

8.2.4 Edge deformation produced by vertical toughening

The tongs used to suspend the glass during toughening can result in surface depressions, known as tong marks (see Figure 6). The centres of the tong marks may be situated up to a maximum of 20 mm in from the edge. A deformation of the edge less than 2 mm can be produced in the region of the tong mark and there can also be an area of optical distortion. These deformations shall be included in the tolerances in Table 2.

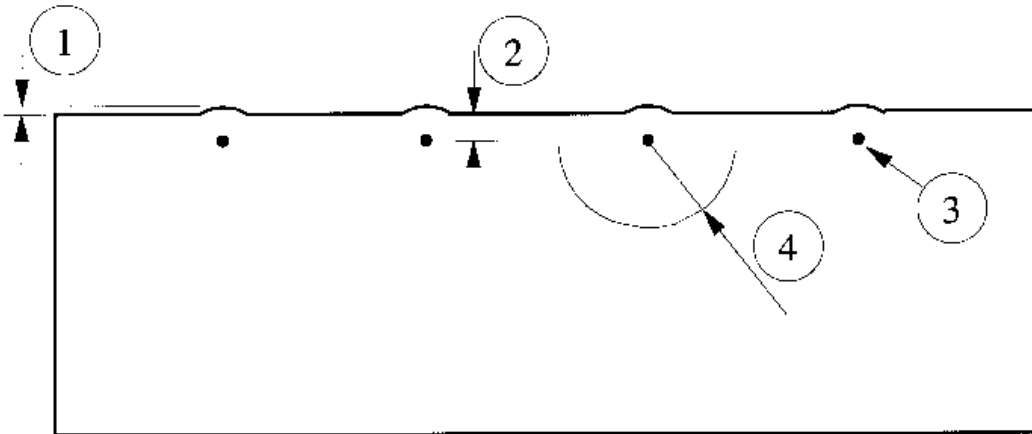

Key

- 1 deformation
- 2 up to 20 mm
- 3 tong mark
- 4 100 mm radius maximum area of optical distortion

Figure 6 — Tong mark deformation

8.3 Flatness

8.3.1 General

By the very nature of the toughening process, it is not possible to obtain a product as flat as annealed glass. The difference depends on the nominal thickness, the dimensions and the ratio between the dimensions. Therefore a distortion known as overall bow may occur. There are two kinds of bow (see Figure 7):

- overall or general bow;
- local bow.

NOTE 1 Overall bow can, in general, be accommodated by the framing system.

NOTE 2 Local bow needs to be allowed for in the glazing materials and the weather seals. For special requirements the manufacturers should be consulted.


8.3.2 Measurement of overall bow

The pane of glass shall be placed in a vertical position and supported on its longer side by two load bearing blocks at the quarter points (see Figure 8).

The deformation shall be measured along the edges of the glass and along the diagonals, as the maximum distance between a straight metal ruler, or a stretched wire, and the concave surface of the glass (see Figure 7).

The value for the bow is then expressed as the deformation, in millimetres, divided by the measured length of the edge of the glass, or diagonal, in millimetres, as appropriate.


The measurement shall be carried out at room temperature.

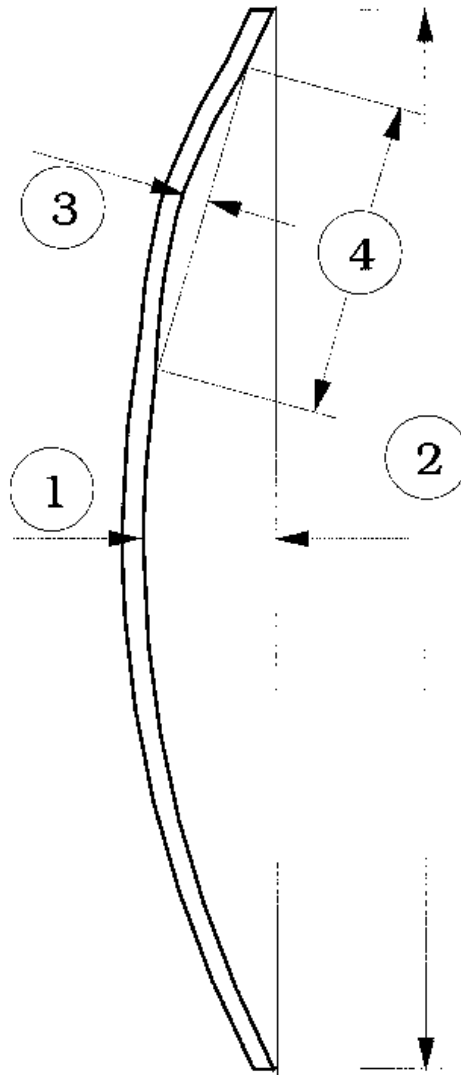

Key

- 1 deformation for calculating overall bow
- 2 B , or H , or diagonal length
- 3 local bow
- 4 300 mm length

Figure 7 — Representation of overall and local bow

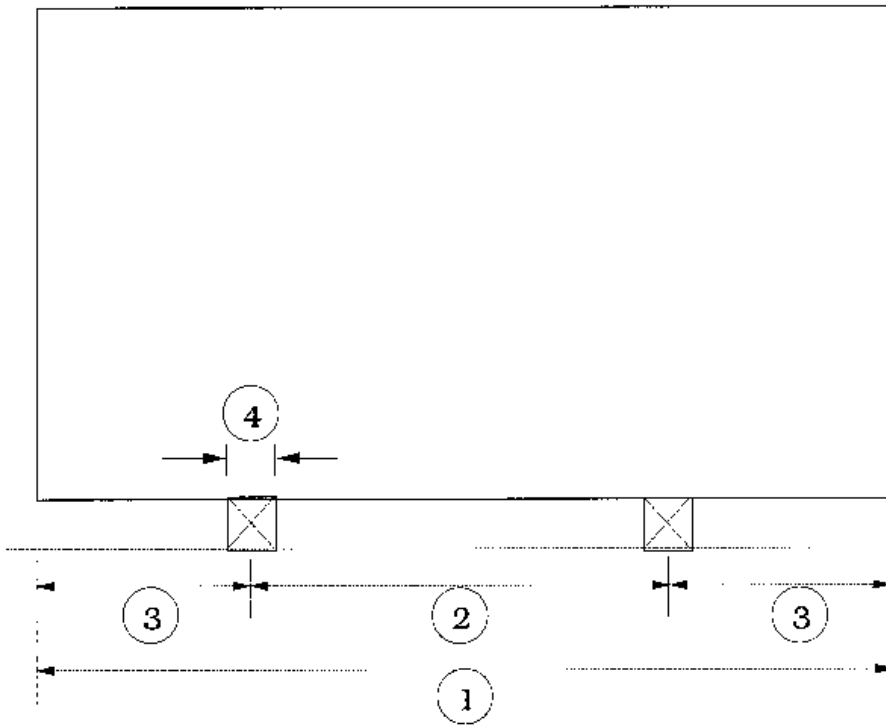

Key

- 1 B or H
- 2 $(B$ or $H)/2$
- 3 $(B$ or $H)/4$
- 4 maximum 100 mm

Figure 8 — Support conditions for the measurement of overall bow

8.3.3 Measurement of local bow

Local bow can occur over relatively short distances on the edges of the glass. Local bow shall be measured over a limited length of 300 mm by using a straight ruler, or a stretched wire, parallel to the edge at a distance of 25 mm from the edge of the glass (see Figure 7).

Local bow is expressed as millimetres / 300 mm length.

For patterned glass, local bow shall be determined by using a straight ruler resting on the high points of the pattern and measuring to a high point of the pattern.

8.3.4 Limitation on overall and local bow

The maximum allowable values for the overall bow, when measured according to 8.3.2, and local bow, when measured according to 8.3.3, for glass without holes and/or notches and/or cut-outs shall not exceed those given in Table 3.

Table 3 — Maximum values for overall and local bow

Toughening process	Type of glass	Maximum values	
		Overall bow mm/mm	Local bow mm/300 mm
Horizontal	Float to EN 572-2	0,003	0,5
	Others	0,004	0,5
Vertical	All	0,005	1,0

9 Edge work, holes, notches and cut-outs

9.1 Warning

WARNING — Heat soaked thermally toughened soda lime silicate safety glass should not be cut, sawn, drilled or edge worked after toughening.

9.2 Edge working of glass for toughening

Every glass that is to be thermally toughened shall be edge worked prior to toughening.

The simplest type of edge working is the arrissed edge (see Figure 9). Other common types are shown in Figures 10 to 12. For specialist edge work, such as 'water jet cutting', the manufacturers should be consulted.

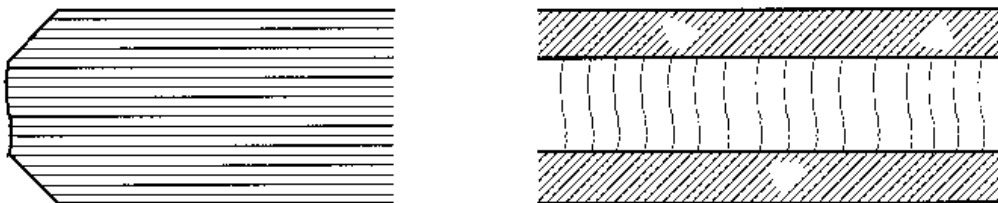


Figure 9 — Arrissed edge (with blank spots)

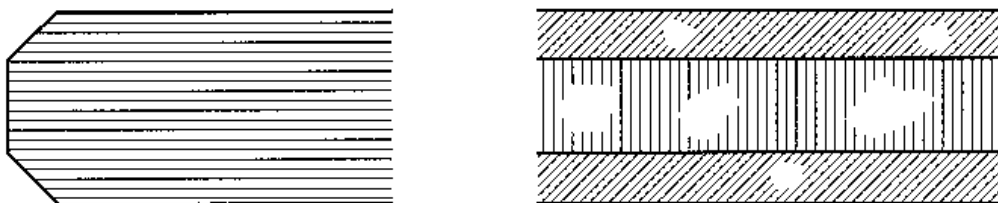


Figure 10 — Ground edge (with blank spots)

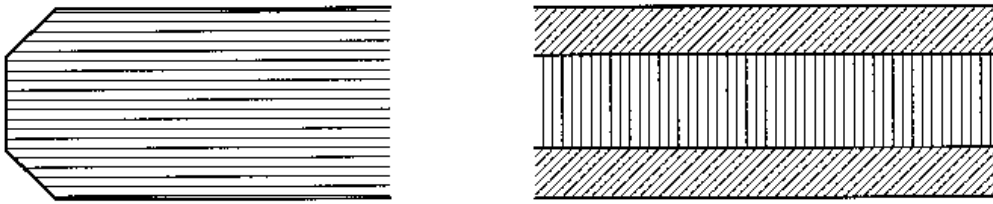


Figure 11 — Smooth ground edge (no blank spots)



Figure 12 — Polished edge

9.3 Profiled edges

Various other edge profiles can be manufactured with different types of edgework.

9.4 Round holes

9.4.1 General

This European Standard considers only round holes in glass that is not less than 4 mm nominal thickness. The manufacturers should be consulted about edge working of holes.

9.4.2 Diameter of holes

The diameter of holes, \varnothing , shall not be less than the nominal thickness of the glass. For smaller holes, the manufacturers should be consulted.

9.4.3 Limitations on position of holes

In general, the limitations on hole positions relative to the edges of the glass pane, the corners of the glass pane and to each other depends on:

- nominal glass thickness (d);
- dimensions of the pane (B , H);
- hole diameter (\varnothing);
- shape of the pane;
- number of holes.

The recommendations given below are those which are normally available and are limited to panes with a maximum of 4 holes.

- 1) The distance, a , of the edge of a hole to the glass edge should be not less than $2d$.

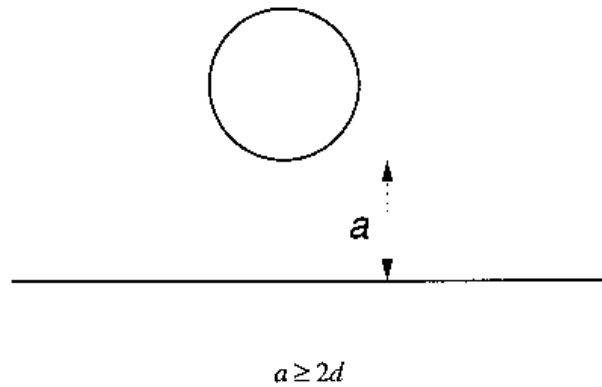


Figure 13 — Relationship between hole and edge of pane

- 2) The distance, b , between the edges of two holes should be not less than $2d$.

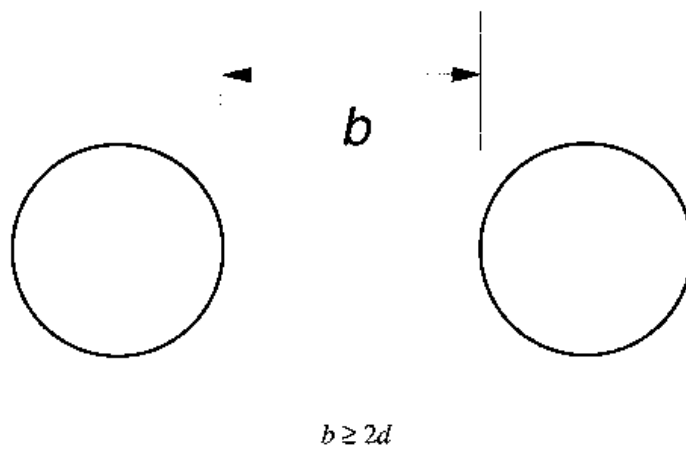


Figure 14 — Relationship between two holes

3) The distance, c , of the edge of a hole to the corner of the glass should be not less than $6d$.

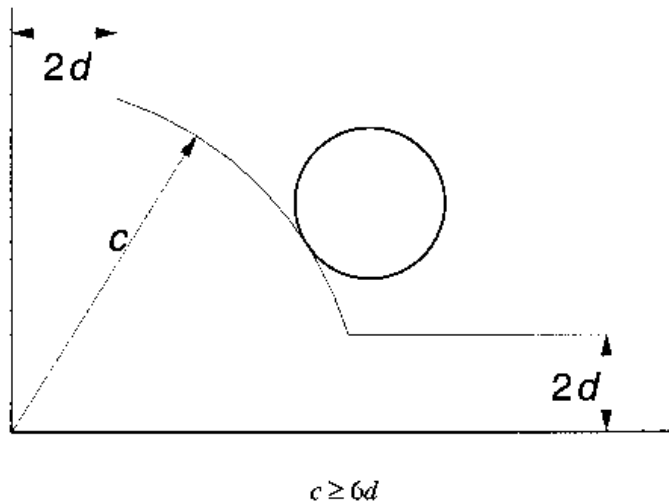


Figure 15 — Relationship between hole and corner of pane

NOTE If one of the distances from the edge of the hole to the edge of the glass is less than 35 mm, it can be necessary to position the hole asymmetrically with respect to the corner. The manufacturer should be consulted.

9.4.4 Tolerances on hole diameters

The tolerances on hole diameters are given in Table 4.

Table 4 — Tolerances on hole diameters

Dimensions in millimetres

Nominal hole diameter, \varnothing	Tolerances
$4 \leq \varnothing \leq 20$	$\pm 1,0$
$20 < \varnothing \leq 100$	$\pm 2,0$
$100 < \varnothing$	consult the manufacturer

9.4.5 Tolerances on position of holes

The tolerances on positions of holes are the same as the tolerances on the width, B , and the length, H (see Table 2). The positions of holes are measured in two directions at right angles (x - and y -axes) from a datum point to the centre of the holes. The datum point is generally chosen as a real or virtual corner of the pane (see Figure 16 for examples).

The position of a hole (X,Y) is $(x \pm t, y \pm t)$, where x and y are the required dimensions and t is the tolerance from Table 2.

NOTE The manufacturer should be consulted if tighter tolerances on hole positions are required.

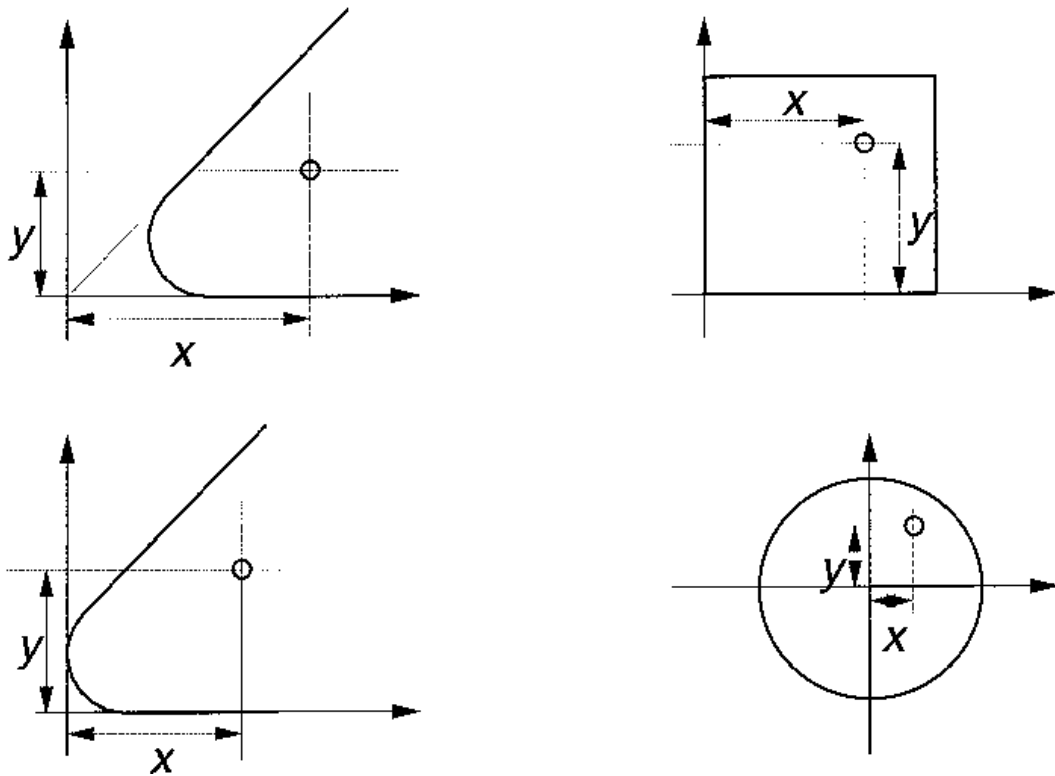


Figure 16 — Examples of the positioning of holes relative to the datum point

9.5 Notches and cut-outs

Many configurations of notches and cut-outs can be supplied.

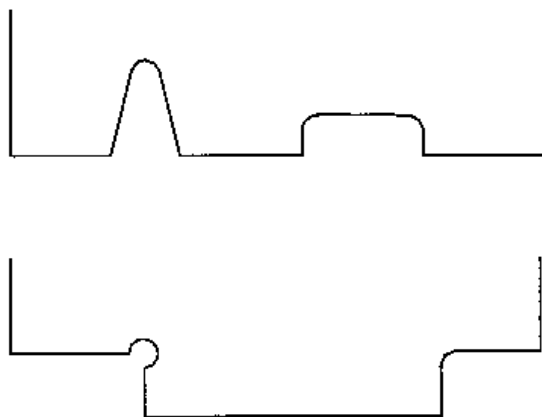


Figure 17 — Examples of notches and cut-outs

The manufacturer should be consulted about edge working of notches and cut-outs.

9.6 Shaped panes

Many non-rectangular shapes can be manufactured and manufacturers should be consulted.

10 Fragmentation test

10.1 General

The fragmentation test determines whether the glass breaks in the manner prescribed for a heat soaked thermally toughened soda lime silicate safety glass.

10.2 Dimensions and number of test specimens

The dimensions of the test specimens shall be 360 mm × 1 100 mm, without holes, notches or cut-outs.

Five specimens shall be tested.

10.3 Test procedure


Each test specimen shall be impacted, using a pointed steel tool, at a position 13 mm in from the longest edge of the test specimen at the mid-point of that edge, until breakage occurs (see Figure 18).

NOTE The fragmentation characteristics of heat soaked heat soak thermally heat soak toughened soda lime silicate glass are unaffected by temperatures between -50 °C and +100 °C.

Examples of steel tools are a hammer of about 75 g mass, a spring loaded centre punch, or other similar appliance with a hardened point. The radius of curvature of the point should be approximately 0,2 mm.

The test specimen shall be laid flat on a table without any mechanical constraint. In order to prevent scattering of the fragments, the specimen shall be simply held at the edges, e.g. by a small frame, adhesive tape etc., so that the fragments remain interlocked after breakage yet extension of the specimen is not hindered.

Dimensions in millimetres

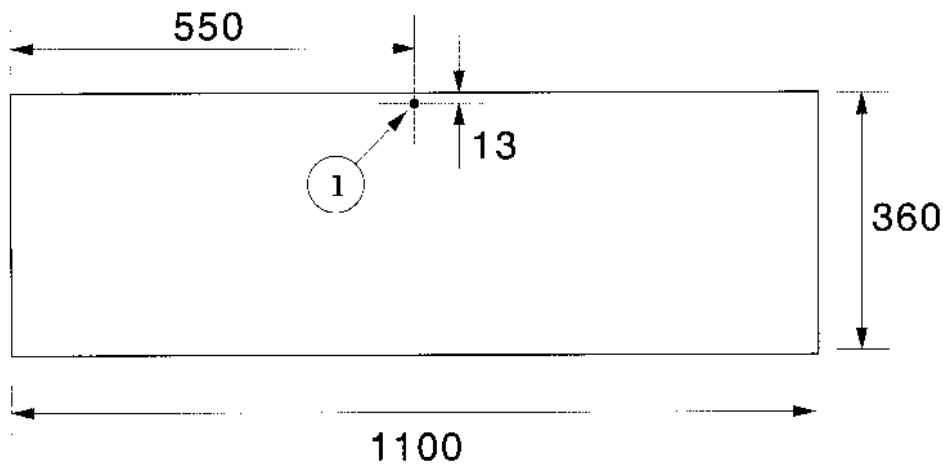

Key

1 impact point

Figure 18 — Position of impact point


For heat soaked thermally toughened soda lime silicate safety glass manufactured by vertical toughening, the impact point shall not be on the tong mark edge.

10.4 Assessment of fragmentation

The particle count and measuring of the dimensions of the largest particle shall be made between 4 min to 5 min after fracture. An area of radius 100 mm, centred on the impact point, and a border of 25 mm, round the edge of the test specimen (see Figure 19), shall be excluded from the assessment.

The particle count shall be made in the region of coarsest fracture (the aim being to obtain the minimum value). The particle count shall be made by placing a mask of $(50 \pm 1) \text{ mm} \times (50 \pm 1) \text{ mm}$ on the test piece (see annex C). The number of crack-free particles within the mask shall be counted. A particle is 'crack-free' if it does not contain any cracks which run from one edge to another (see Figure 20).

Dimensions in millimetres

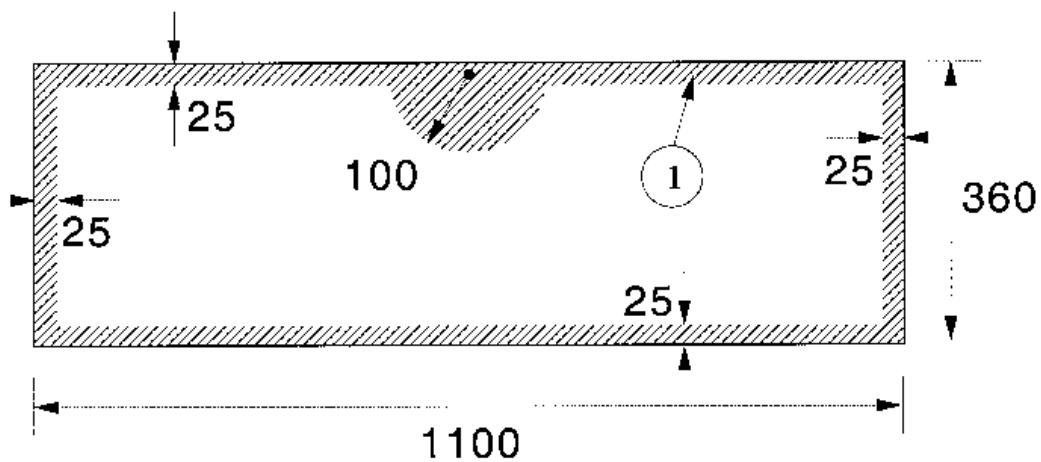

Key

1 excluded area

Figure 19 — Area to be excluded from the particle count determination and largest particle measurement

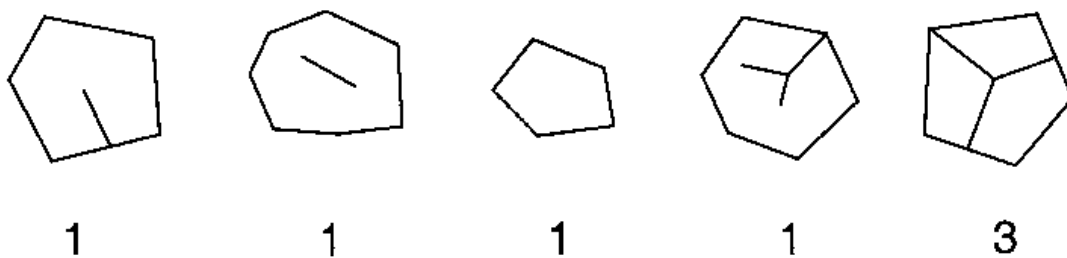


Figure 20 — Examples of crack-free particles and the assessment regarding the number

In the particle count, all particles wholly contained within the area of the mask shall be counted as one particle each and all the particles which are partially within the mask shall be counted as 1/2 particle each (see Annex C).

10.5 Minimum values from the particle count

In order to classify a glass as a heat soaked thermally toughened soda lime silicate safety glass, the particle count of each test specimen shall not be less than the values given in Table 5.

Table 5 — Minimum particle count values

Glass type	Nominal thickness (<i>d</i>) mm	Minimum particle count
Float and drawn sheet	3	15
	4 to 12	40
	15 to 19	30
Patterned	4 to 10	30

10.6 Selection of the longest particle

The longest particle shall be chosen from the body of the test specimen. It shall not be in the excluded area (see 10.4).

10.7 Maximum length of longest particle

In order to classify the glass as heat soaked thermally toughened soda lime silicate safety glass, the length of the longest particle shall not exceed 100 mm.

11 Other physical characteristics

11.1 Optical distortion

11.1.1 Heat soaked thermally toughened soda lime silicate safety glass produced by vertical toughening

The tong marks can produce additional optical distortion which is generally in an area of radius 100 mm centred on the tong mark (see Figure 6).

11.1.2 Heat soaked thermally toughened soda lime silicate safety glass produced by horizontal toughening

While the hot glass is in contact with the rollers during the toughening process, a surface distortion is produced by a reduction in surface flatness, known as 'roller wave'. Roller wave is generally noticed in reflection. Glass which is thicker than 8 mm can show signs of small imprints in the surface ('roller pick-up').

11.2 Anisotropy (iridescence)

The toughening process produces areas of different stress in the cross section of the glass. These areas of stress produce a bi-refracting effect in the glass, which is visible in polarised light.

When heat soaked thermally toughened soda lime silicate safety glass is viewed in polarised light, the areas of stress show up as coloured zones, sometimes known as 'leopard spots'.

Polarised light occurs in normal daylight. The amount of polarised light depends on the weather and the angle of the sun. The bi-refrangent effect is more noticeable either at a glancing angle or through polarised spectacles.

11.3 Thermal durability

The mechanical properties of heat soaked thermally toughened soda lime silicate safety glass are unchanged for continuous service up to 250 °C and are unaffected by sub-zero temperatures. Heat soaked thermally toughened soda lime silicate safety glass is capable of resisting both sudden temperature changes and temperature differentials up to 200 K.

11.4 Mechanical strength

The value of mechanical strength can only be given as a statistical value associated with a particular probability of breakage and with a particular type of loading.

The mechanical strength values apply to quasi-static loading over a short time, e.g. wind loading, and relate to a 5 % probability of breakage at the lower limit of the 95 % confidence interval. The values for different types of glass are listed in Table 6.

Table 6 — Values for the mechanical strength of heat soaked thermally toughened soda lime silicate safety glass

Type of glass	Values for mechanical strength N/mm ²
Float: Clear Tinted Coated	120
Enamelled float (based on the enamelled surface in tension)	75
Patterned glass and drawn sheet	90

NOTE The values in Table 6 represent the strength of heat soaked thermally toughened soda lime silicate safety glass (4 mm and thicker) that meets the requirements of 10.5.

11.5 Classification of performance under accidental human impact

Heat soaked thermally toughened soda lime silicate safety glass can be classified, as to its performance under accidental human impact, by testing in accordance with EN 12600.

12 Marking

Heat soaked thermally toughened soda lime silicate safety glass conforming to this European Standard shall be permanently marked. The marking shall give the following information:


- name or trademark of manufacturer;
- number of this European Standard: EN 14179-1.

Annex A
(normative)

Heat soak process system calibration test

A.1 Calibration criteria

The heat soak process system shall comply with the time/temperature regime as shown in Figure A.1. The system shall be capable of meeting in the regime at both 100 % and 10 % load.

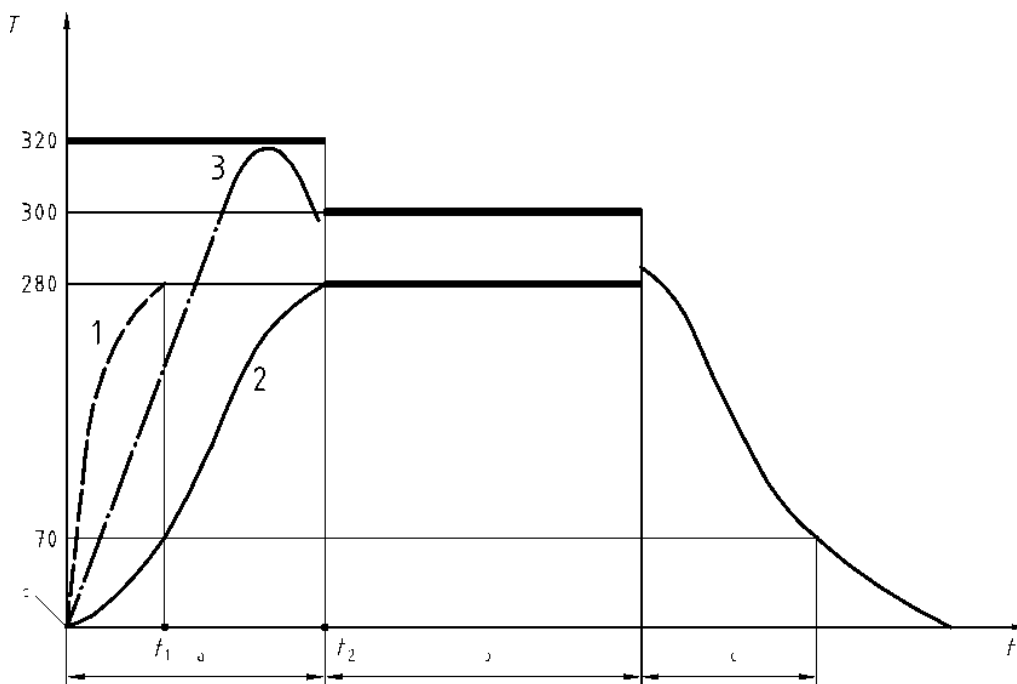

Key

- | | | | |
|-------|--|---|---------------------|
| T | Glass temperature at any point, °C | 3 | glass temperature |
| t | time, h | d | ambient temperature |
| t_1 | time for the first glass to reach 280 °C | a | heating phase |
| t_2 | time for the last glass to reach 280 °C | b | holding phase |
| 1 | first glass to reach 280 °C | c | cooling phase |
| 2 | last glass to reach 280 °C | | |

Figure A.1 — Time/temperature regime as calibration criteria

A.2 Loading of oven and position for glass surface temperature measurement

Figures A.2 to A.9 show the appropriate pattern of stillage(s) loading and thermocouple placements for ovens, which take 1, 2, 6, 8 or 9 stillage(s).

The duration of the heating phase is dependent on the capacity of the oven and the level of load being used.

NOTE 1 Full load will be dependent on glass size, thickness and oven volume. Generally full load will be defined based on 6 mm or 8 mm thickness.

The separation of the glasses shall be specified as shall also the type, position, material and shape of the separators. The separation of the glasses shall be constant on the stillage(s).

The minimum separation used during calibration is the minimum separation that can be employed during the manufacturing process.

NOTE 2 Generally, a minimum separation of 20 mm is recommended.

A.3 Procedure

The measurements of the air temperature in the oven and the glass surface temperatures shall be carried out when the furnace is fully loaded. They shall be repeated for a 10 % loading.

The oven air temperature is monitored by a control element, which is located near the air egress. The measurement of the glass surface temperatures is carried out by thermocouples that are stuck, with good thermal contact, to the glass surfaces.

At the beginning of the calibration, the air temperature in the oven shall not exceed 35 °C.

During the heating phase the oven shall be heated up until the last glass surface temperature reaches 280 °C.

During the heating phase the glass temperature shall not exceed 320 °C at any place.

During the heating phase the following parameters shall be recorded:

- T_c temperature of the control element (at any time);
- t_1 time for the first thermocouple and a glass to reach a temperature of 280 °C;
- T_{c1} temperature of control element at time t_1 ;
- t_2 time for the last thermocouple and a glass to reach a temperature of 280 °C;
- T_{cmax} maximum temperature of the control element during the heating phase;
- t_{cmax} time at which T_{cmax} occurs;
- T_{glass} temperature of the glass surfaces, measured by the thermocouples (at any time) (see Figures A.2 to A.9).

The holding phase starts at time t_2 and shall last for a period of 2 hours. The glass surface temperatures T_{glass} shall remain within the range 290 °C \pm 10 °C. The control element temperature T_c shall be recorded.

The cooling phase starts at time $t_2 + 2$ h. The control element temperature T_c shall be recorded. The oven can be opened when T_c reaches 70 °C.

A.4 Records

The test parameters:

- t_1, T_{c1}
- t_{cmax}, T_{cmax}

EN 14179-1:2005 (E)

- t_2
- T_c, T_{glass}
- glass separation distance
- separator position, material, shape
- stillage(s) configuration


shall be recorded.

A.5 Interpretation of the calibration test

If the conditions for temperatures laid down in A.1 are not met then the oven shall not be regarded as calibrated.

Only ovens, which meet the calibration criteria as laid down in A.1 at full and 10 % load may be used for the heat soak process cycle during manufacture. The longer of the two times $t_{2,1}$ (full load) or $t_{2,2}$ (10 % load) shall be used for regular production.

The heat soak process system used for manufacture shall comply with the details of the system as calibrated.

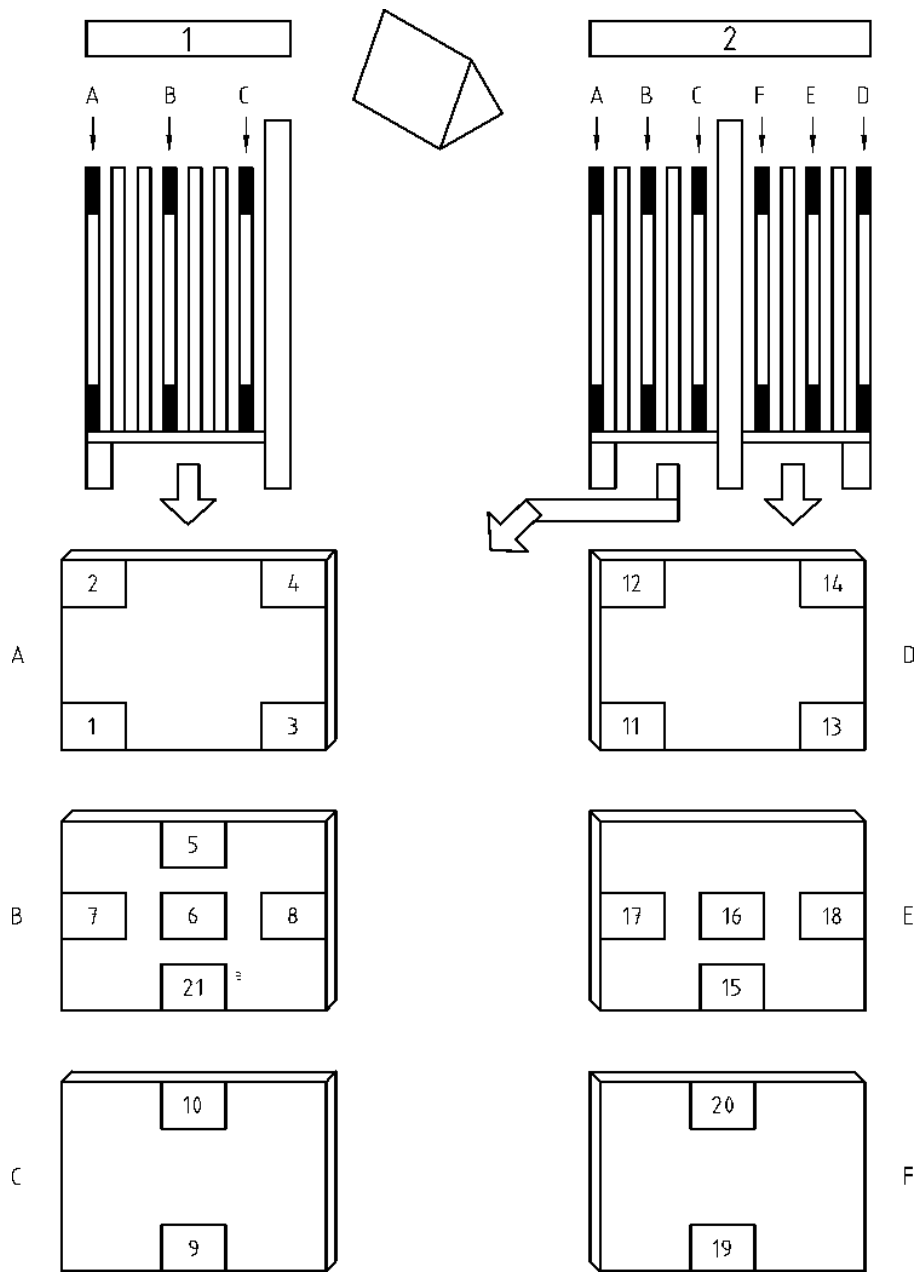


NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Key

- ^a is only used for mono side stillages
- 1 mono side stillage
- 2 double sided stillage

Figure A.2 — 1st category – 1 stillage – full load

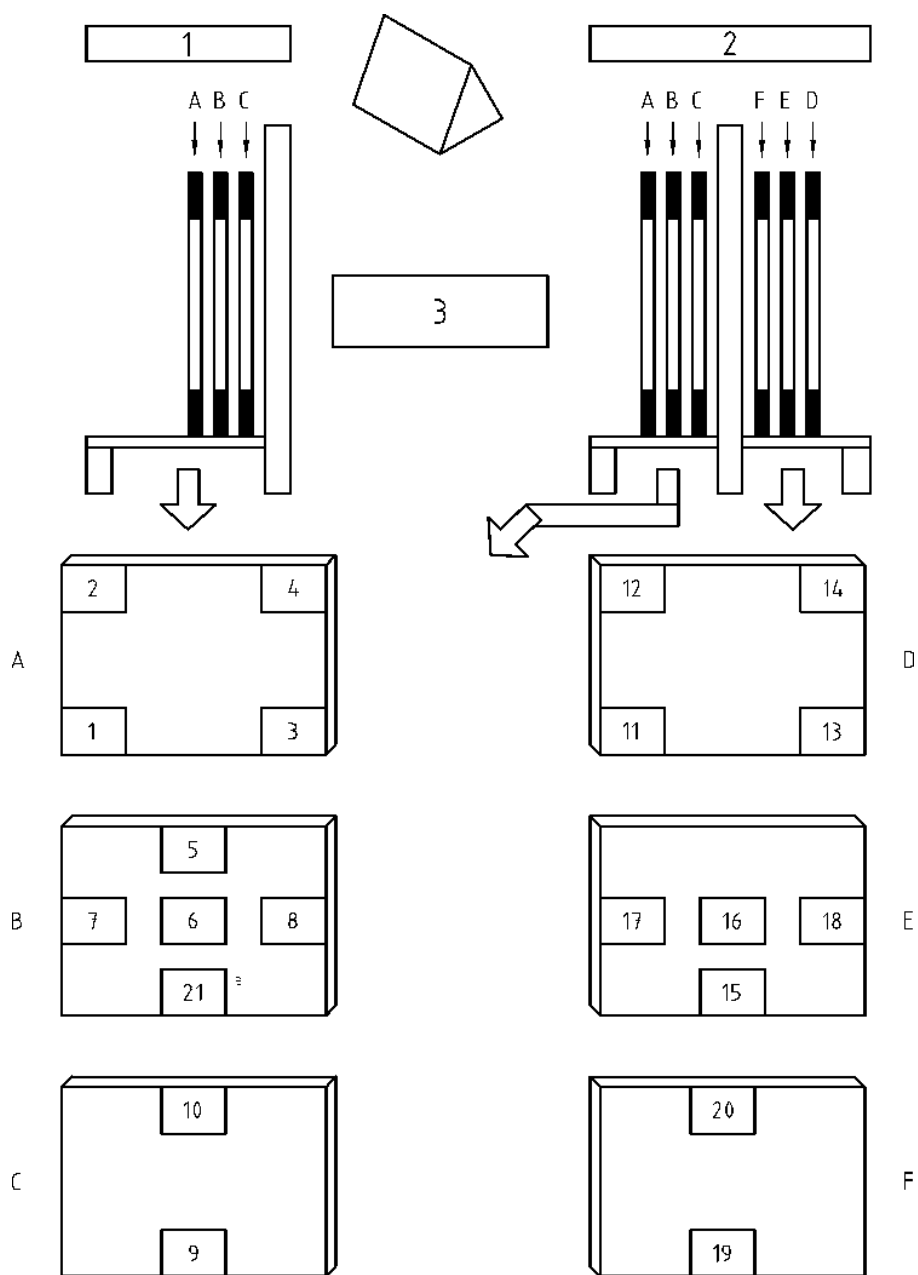


NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Key


- ^a is only used for mono side stillages
- 1 mono side stillage
- 2 double sided stillage
- 3 on the stillage: minimum 3 glasses in parallel side by side

Figure A.3 — 1st category – 1 stillage – 10 % load

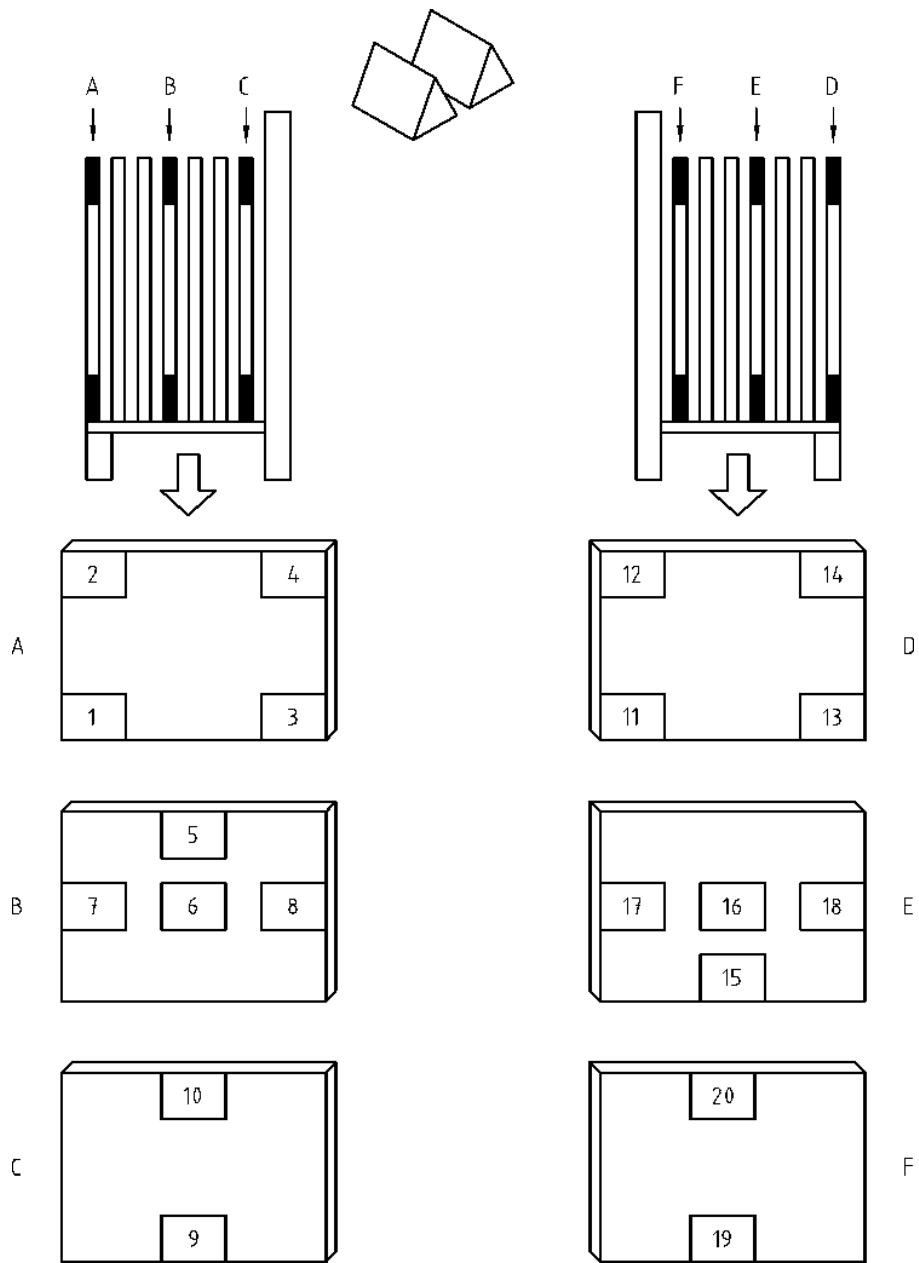

NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Figure A.4 — 2nd category – 2 mono side stillages – full load

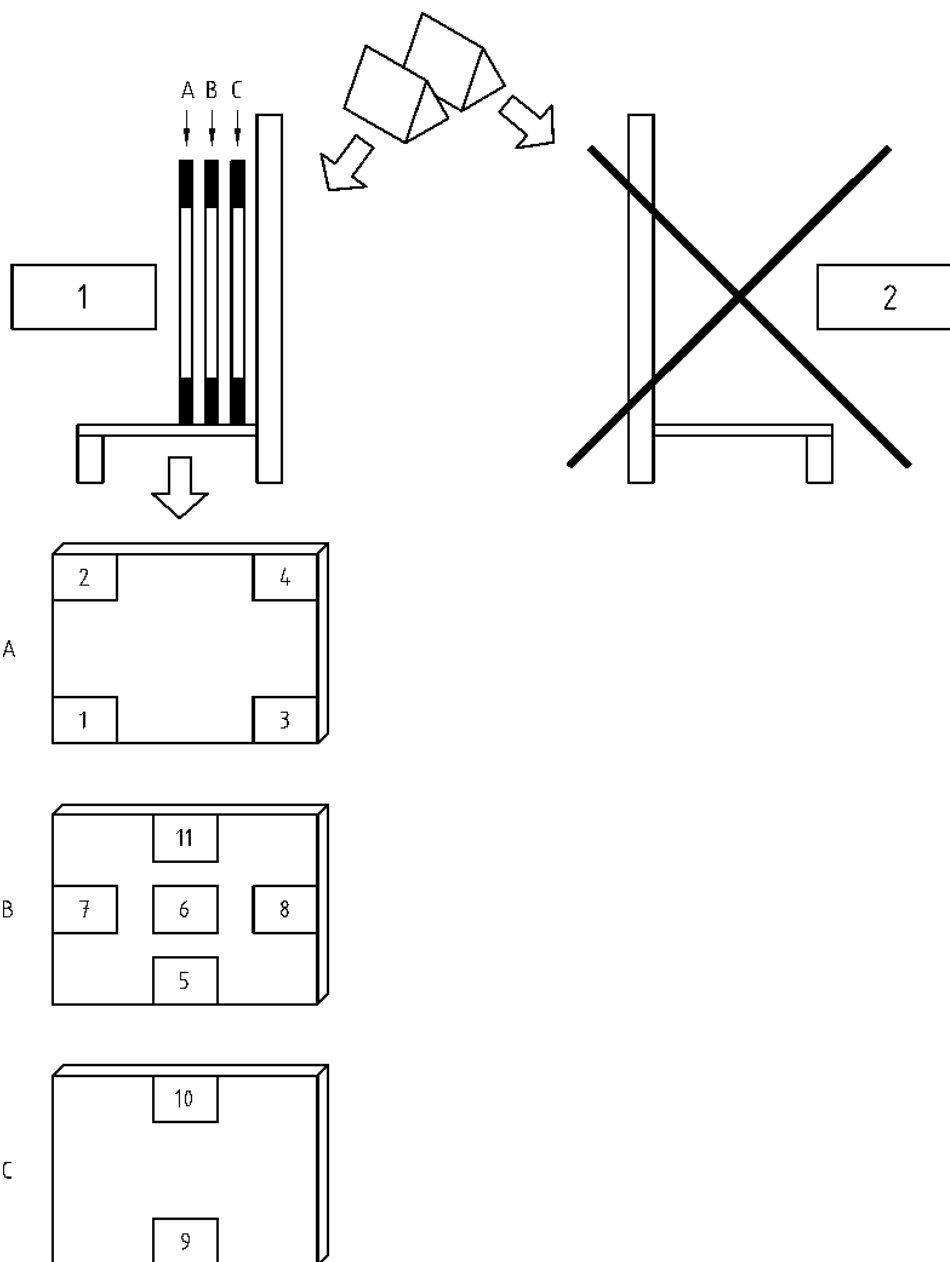


NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Key


- 1 1st stillage: minimum 3 glasses in parallel
- 2 don't use the 2nd stillage

Figure A.5 — 2nd category – 2 mono side stillages – 10 % load

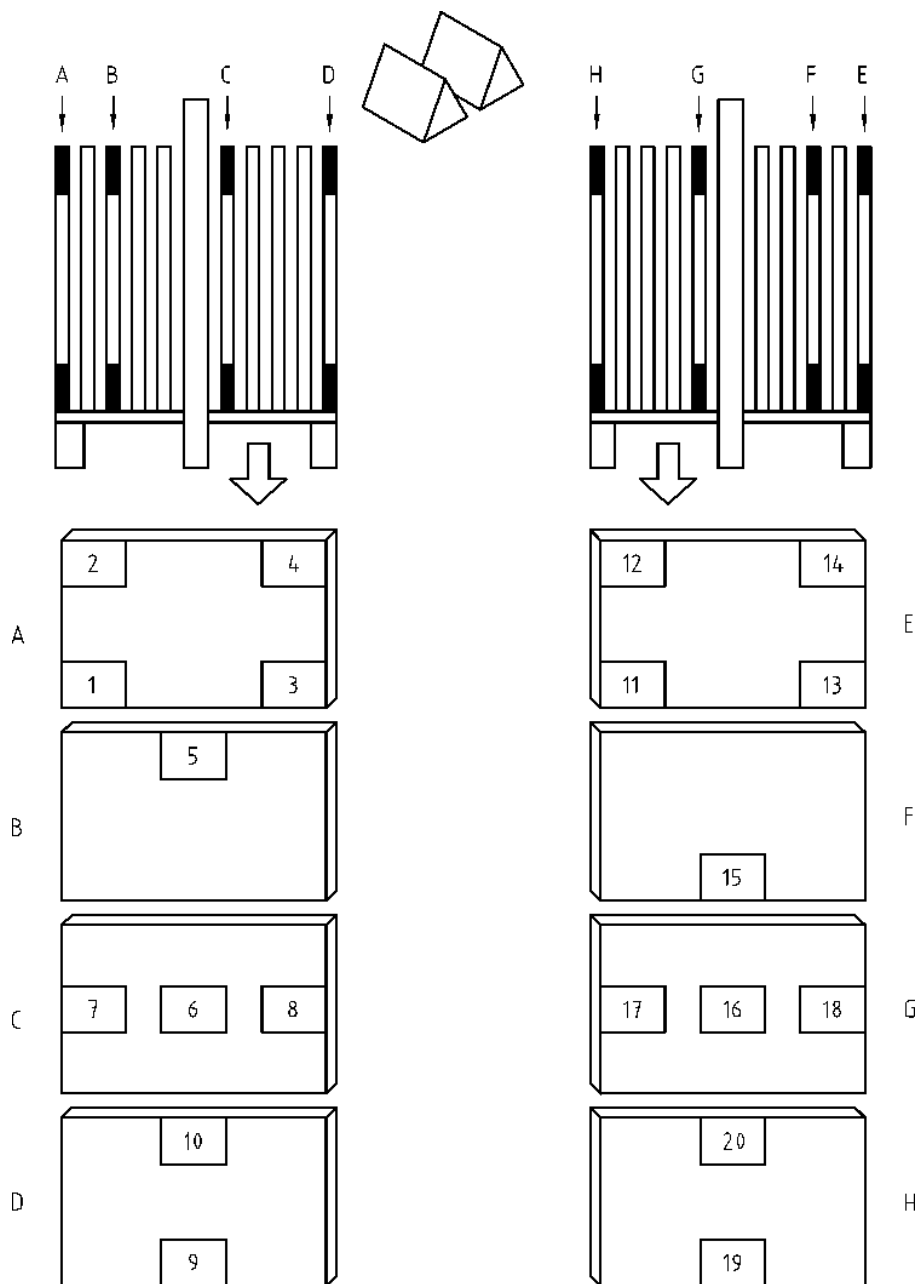

NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Figure A.6 — 2nd category – 2 double sided stillages – full load

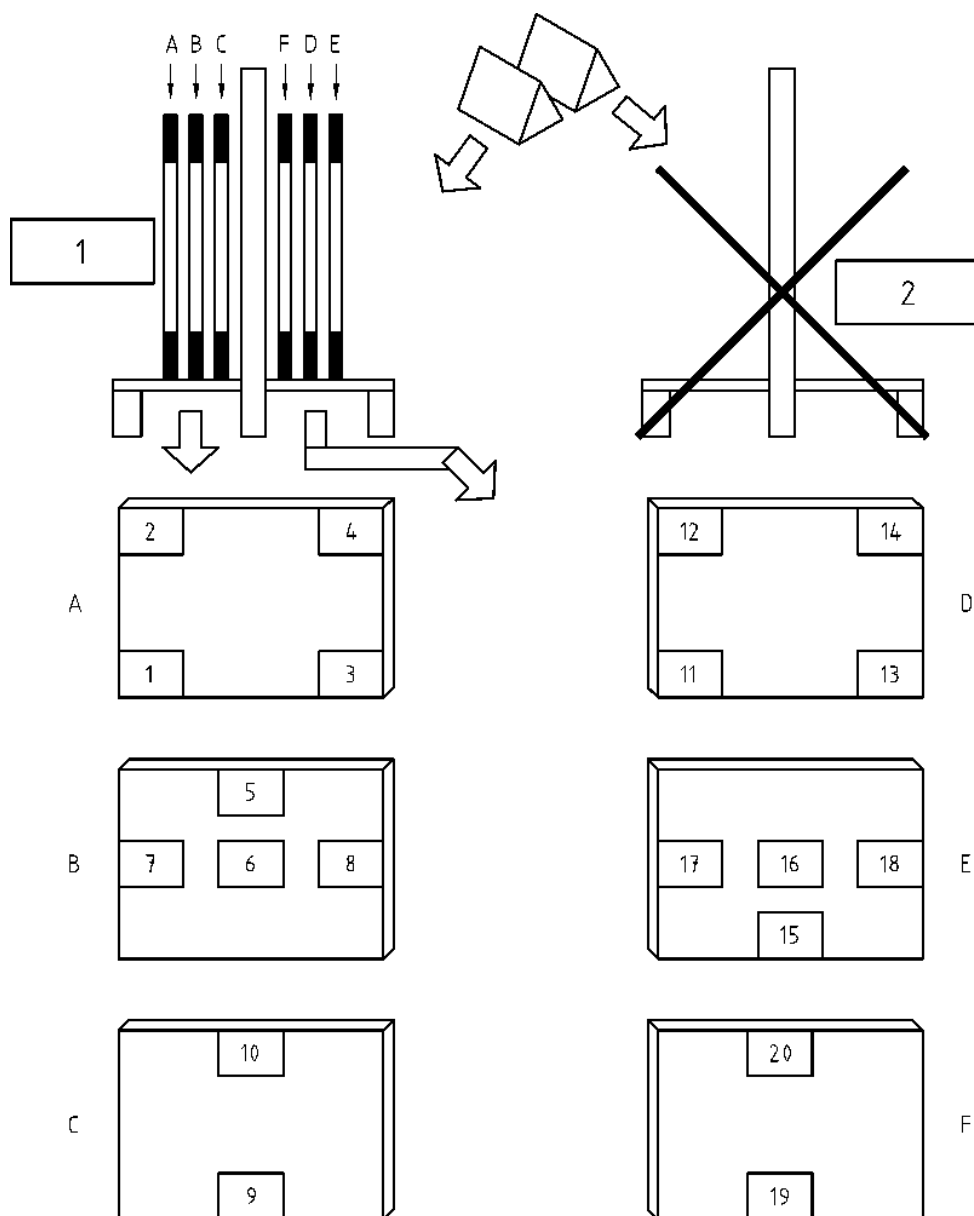


NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Key


- 1 1st stillage: minimum 3 glasses in parallel side by side
- 2 don't use the 2nd stillage

Figure A.7 — 2nd category – 2 double sided stillages – 10 % load

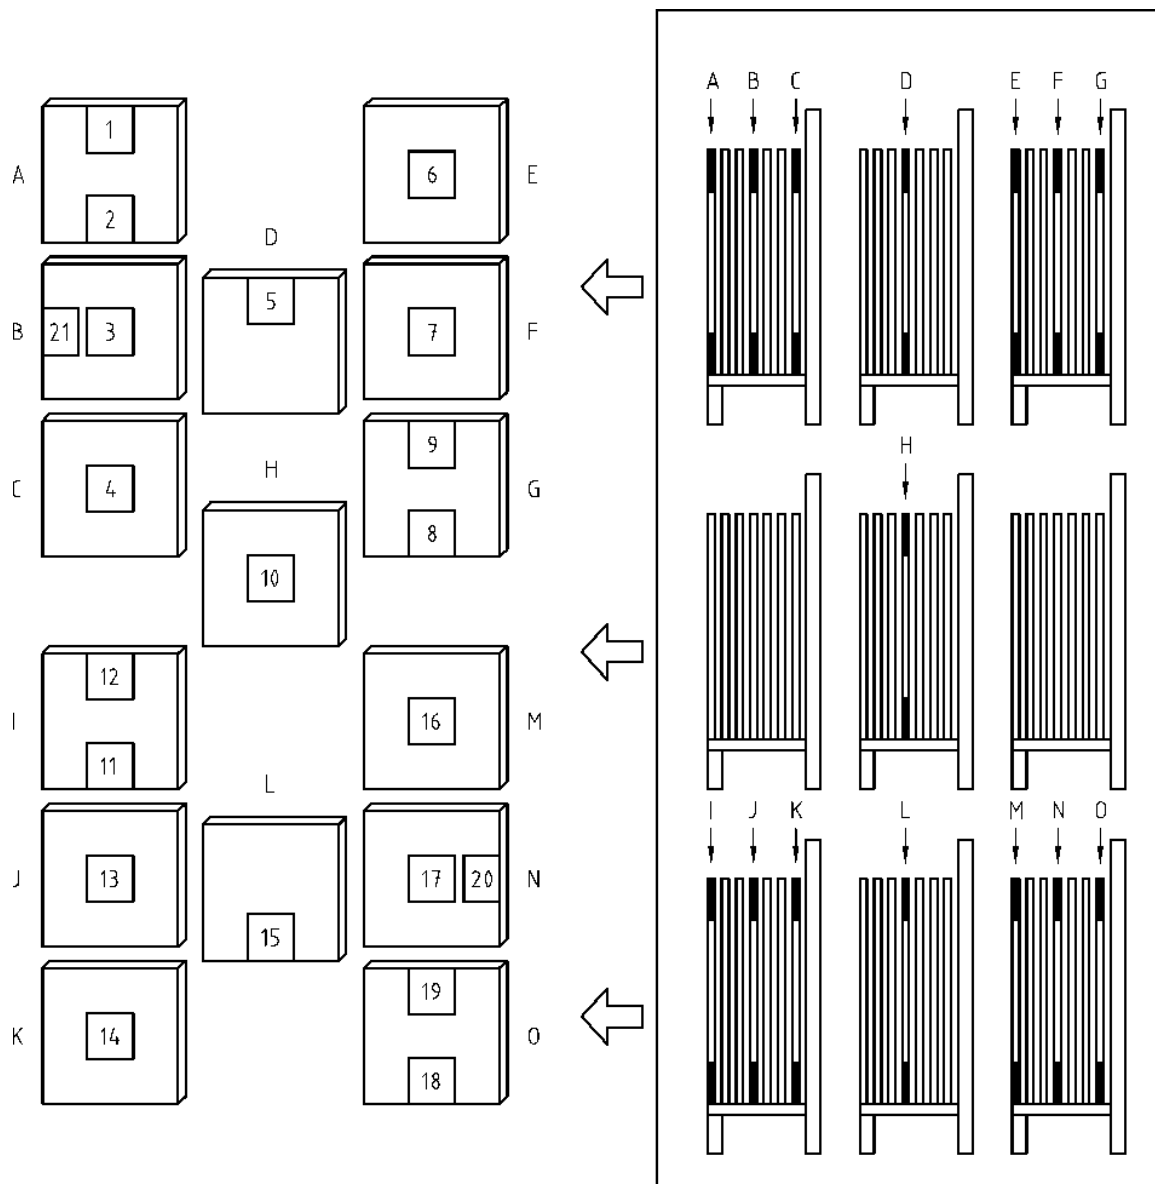

NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Figure A.8 — 3rd category – 6 or 8 or 9 ... stillages – full load

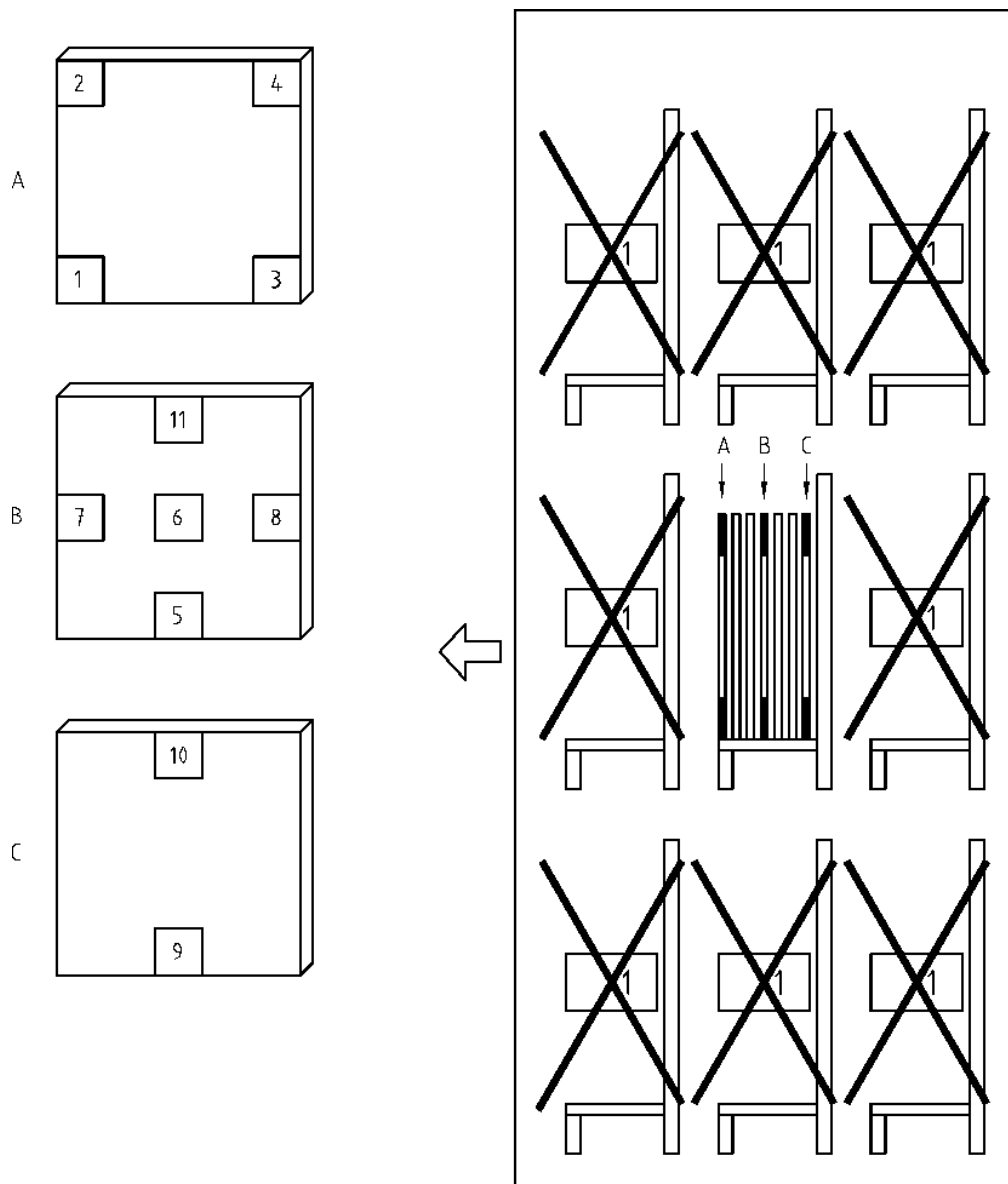

NOTE Thermocouples should not be fixed nearer to the edge than 25 mm.

Key

1 don't use

Figure A.9 — 3rd category – 6 or 8 or 9 ... stillages – 10 % load

Annex B
(informative)

Curved heat soaked thermally toughened soda lime silicate safety glass

Curved (in the UK also called bent) heat soaked thermally toughened soda lime silicate safety glass has been deliberately given a specific profile during the course of manufacture. It is not included in this European Standard since there is insufficient data available to standardise the product. However, the information given in this European Standard on thickness, edge work and fragmentation is also applicable to curved heat soaked thermally toughened soda lime silicate safety glass.

The information on the heat soak process cycle is also applicable. However, extreme care should be taken to ensure that the curved shape does not interfere with the airflow.

Annex C
(informative)

Examples of particle count


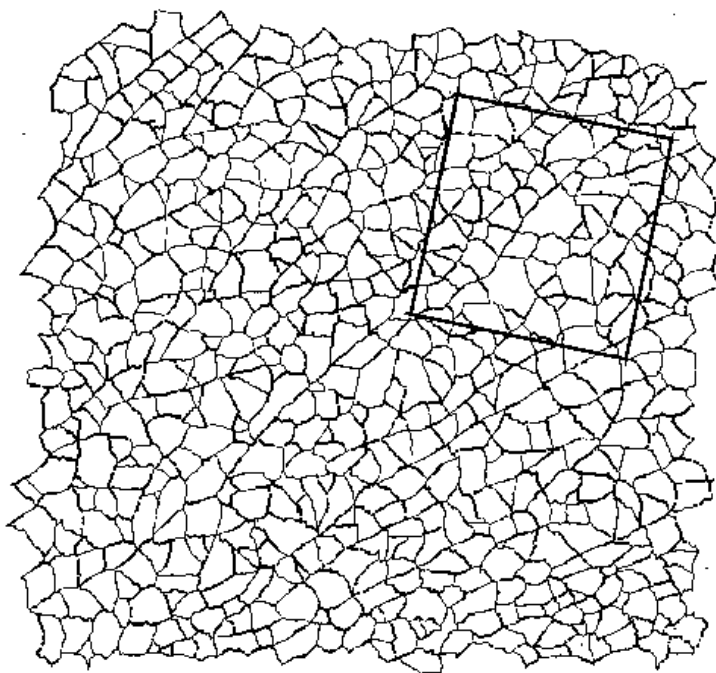



Figure C.1 — Select the area of coarsest fracture, place the template on the test specimen and draw round the template

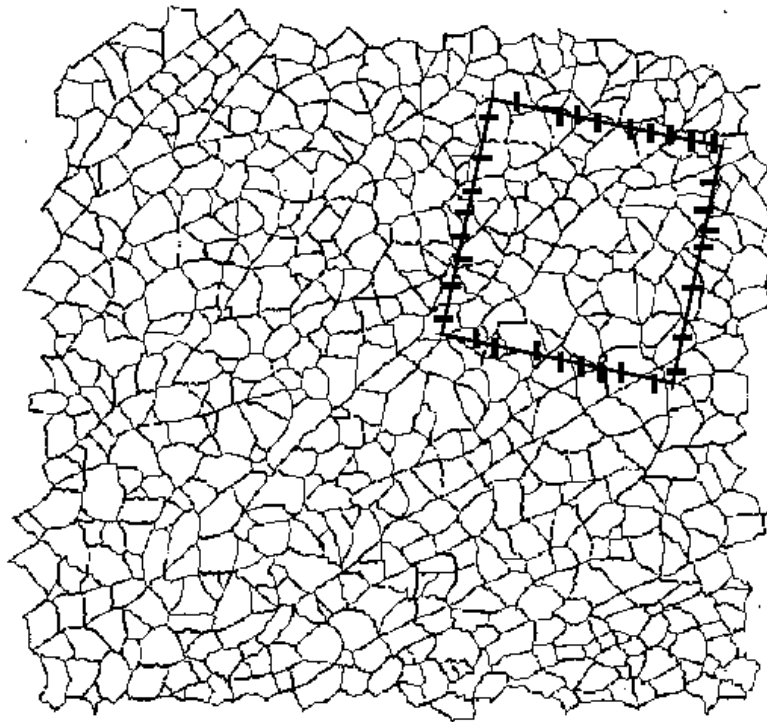

Key

Number of perimeter particles = $32/2 = 16$

Figure C.2 — Mark and count the perimeter fragments as 1/2 particle each

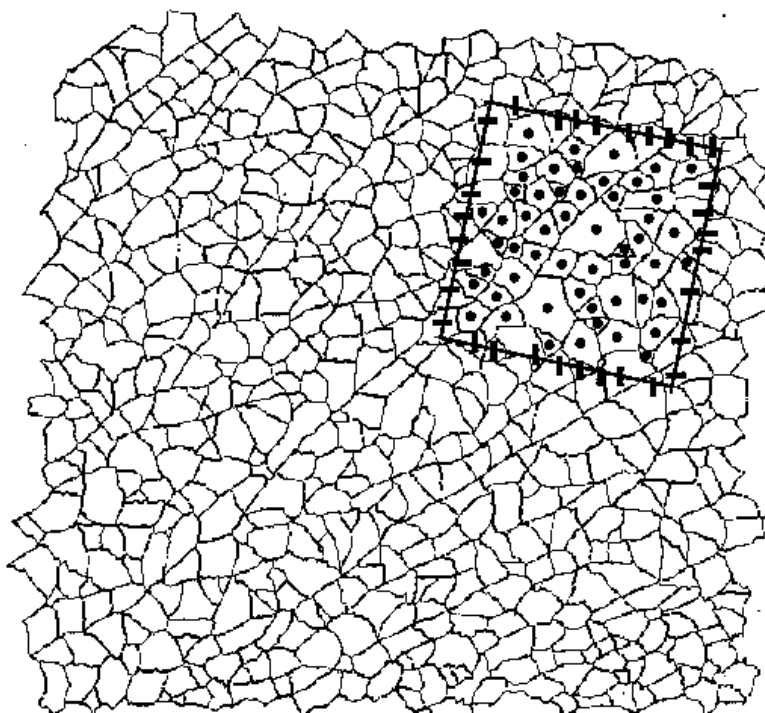

Key

Number of central particles = 53

Total number of particles = 16 + 53 = 69

Figure C.3 — Mark and count the central fragments and add these to the perimeter count to obtain the particle count for the specimen

Bibliography

- [1] BALLANTYNE, E.R.: "Fracture of toughened glass Wall cladding, ICI house Melbourne", CSIRO, Div. O Build. Res. Dpt., 06 (1961) 1–5.
- [2] BARRY J.C.: "A study of nickel sulphide stones in tempered glass", Ultramicroscopy 52, 1993, pp 297–305.
- [3] BORDEAUX, F., KASPER, A., "Optimised Heat Soak Test to eliminate dangerous nickel sulphide stones in heat strengthened and tempered glasses", Proceedings of the ESG annual Meeting «Fundamentals of Glass Science and Technology» June 1997, Växjö, Sweden, pp.255–264.
- [4] BORDEAUX, F., KASPER, A., "Reliable and shorter Heat Soak Test to avoid spontaneous fracture of heat strengthened and tempered glasses" Proceedings of the 5th Glass Processing Days, Tampere - Finland, Sept. 13–15, 1997.
- [5] BORDEAUX, F., DUFFRENE, L., KASPER, A., "Nickelsulfid: Neue Ergebnisse zur Optimierung des Heat Soak Tests", Glastech. Ber. Glass Sci. Technol. 71(1998) S. N27–28 and HVG-Mitteilung Nr. 1908.
- [6] BORDEAUX, F., DUFFRENE, L., KASPER, A., "A shorter Heat Soak test to avoid spontaneous failure of heat strengthened and tempered glass", Proceedings of the 18th International Congress On Glass (ISBN 1-57498-053-X), San Francisco, July 5 - 10, 1998, ICG333-A04-002, pp.7–12.
- [7] BRAUN, W.: "Investigation of formation of nickel sulphides in glass", Proceedings of the 5th ESG conference, Prague, July 1999, pp. A4-54–56.
- [8] BRAUN, W., TESSMANN, E., STACHEL, D.: "Nickel sulphidic inclusions – some examples", Proceedings of the 5th ESG conference, Prague, 1999, pp. A4-38–39.
- [9] BRUNGS, M.P., SUGENG, X.Y.: "Some solutions to the nickel sulphide problem in toughened glass", Glass Tech., Vol. 36 (1995), n04, pp 107–110.
- [10] Carbolite: "Heat soaking eliminates inferior toughened glass", Glass, April 1996, pp 156.
- [11] DUFFRENE, L., KASPER, A., DUBRU, M., "Amélioration du test Heat Soak pour le verre trempé thermique", Verre (ISSN 09847979-185F) 5(2000) N° 6. S.18–21.
- [12] DURCHHOLZ, M., GOER, B., HELMICH, G.: "Method of reproducibly predamaging float glass as a basis to determine the bending strength", Glastech. Ber. Glass sci. Technol. 66(1995) No. 8, pp 251–258.
- [13] EVANS, A.G., MATER, J.: "The role of inclusions in the fracture of ceramic materials", Science, 9(1974) pp 1145.
- [14] HSIAO, C.C.: "Spontaneous fracture of tempered glass", Fracture 1977, Vol. 3, ICF4, Waterlow, Canada, June 19-24, 1977, pp 985–992.
- [15] JACOB, L.: "A new model for the design of window glass plates using fracture mechanics concepts", Proceedings of the Glass Processing Days, 1999, Tampere, Finland, pp. 196–199.
- [16] KASPER, A., "Auswertemethoden für Ergebnisse des Heat-Soak-Tests zur Lösung der Nickelsulfidproblematik in vorgespanntem Glas", Vortrag während der 73. Glastechnischen Tagung der DGG, Halle (Saale), 31.5. – 2.6.1999, Kurzreferate S.196.

EN 14179-1:2005 (E)

- [17] KASPER, A., "Advances in testing tempered glasses in heat soak ovens" Proceedings of the 5th Glass Processing Days (ISBN 952-91-0885-0) (1999) pp.71–75.
- [18] KASPER, A., "Spontanbruch von Einscheiben-Sicherheitsglas am Bau – ein lösbares Problem", Vortrag und Artikel im Tagungsband der VDI-Tagung "Bauen mit Glas" in Baden-Baden, 1./2. März 2000, ISBN 318-091527-7, VDI-Verlag Düsseldorf 2000, pp.219–234.
- [19] KASPER, A., BORDEAUX, F., DUFFRENE, L.: "Nickel sulphide: New Results to Optimise the Heat Soak Test for Tempered Building Glasses", *Glastech. Ber. Glass Sci. Technol.* 73(2000)No. 5 pp.130–142.
- [20] KASPER, A.: Stability of Nickel Sulfide Stones in Glass Melts. Lecture at the 6th International Conference "Advances in Fusion and Processing of Glass" / 74. Glastechnische Tagung, 29. - 31.Mai 2000 in Ulm. "Abstracts" pp. 109–111.
- [21] KISSINGER, H.E.: "The calculation of kinetic properties of phase transitions from differential scanning calorimetry measurements", *J. Res, Nat. Bur. Stand.* 57 (1956), p: 217.
- [22] KRAUSS, M.: Nickelsulfidbildung in Borosilicatschmelzen, (in German) Lecture at the 74. Glastechnische Tagung (DGG), Ulm 2000, Kurzreferate pp. 141–144.
- [23] KULLERUND G., YUND R.A.: "The NiS System and Related Minerals", *J. Petrology*, Vol. 3, Part 1 (1962), p. 126–175.
- [24] LAFFITTE M., BENARD J.: "Stoichiometry and Stability Limits of the Hexagonal NiS", *Comptes rendus hebdomadaires de l'académie des sciences*, 242(1956), pp: 519–521.
- [25] LAFFITTE M.. "Crystal structure and Thermodynamic Properties of Hexagonal NiS", *Bult Soc. Chem.* (1959), p: 1223.
- [26] MERKER, L.: "Zum Verhalten des Nickelsulfids im Glas", *Glastech. Ber.* 47 (1974) 6, pp 116–121.
- [27] PAUL, U., AULICH, U.: "Nach Glasregen am Lafayette: Baustadtrat stellt Ultimatum" (in German), *Berliner Zeitung*, Nr. 280, 01.12.1998.
- [28] POPPOOLA, O.O., COOPER J.J., KRIVEN W.M.: "Microstructural Investigation of fracture-initiating Nickel Sulphide Inclusions in Glass", *Ceram. Eng. Sci. Proc.* 14 (1993) 3–4, pp 184–194.
- [29] STACHEL, D., TESSMANN, E., TRAUFLDER, S., BRAUN, W.: "Non-oxidic inclusions in glass", Proceedings of the 5th ESG conference, Prague, 1999, pp. A4–2–14.
- [30] STACHEL, D.: Nickel sulphidic inclusions with heterogeneous structure. 6th international Conference "Advances in Fusion and Processing of Glass" Ulm, may 2000, "Abstracts" pp. 105–107.
- [31] SWAIN, M.V.: "A fracture mechanics description of the microcracking about NiS inclusions in glass", *J. Non-Crystal. Solids* 38 & 39 (1980) pp 451.
- [32] SWAIN, M.V.: "Nickel sulphide inclusions in glass: An example of microcracking induced by a volumetric expanding phase", *J. Mat. Science* 16 (1981) pp 151–158.
- [33] WAGNER, G, LANG, R.: "Statistische Auswertung von Mess- und Prüfergebnissen." Frankfurt a/M., Deutsche Gesellschaft für Qualität, 1976.
- [34] WAGNER, R.: "Inclusions de sulfure de nickel dans le verre" (in French), *Glastechn. Ber* 50 (1977) Nr. 11, pp 296.
- [35] WALDRON, B.: "NiS: is there a problem?", *Glass*, Nov. 1993, pp 439.

- [36] WILLMOTT, T.: "Nickel sulphide inclusions: Proving the 'myth' can be a reality", *Glass and Glazing*, Oct. 1996, pp 24 and 26.
- [37] "Those window pains", *Time*, October 15, 1973 (author unknown).
- [38] "Nickel sulphide breakage", *Glass Digest*, march 1992, pp 12 (author unknown).
- [39] "Flat glass panels 'explode' in Britain", *American Glass Review*, Nov. 1993, pp 8 (author unknown).
- [40] German Standard DIN 55303, T. 7 (Entwurf Juli 1993): *Statistische Auswertung von Daten, Schätz- und Testverfahren bei zweiparametrischer Weibull-Verteilung*. Berlin: DIN 1993.
- [41] EN 12600, *Glass in building — Pendulum test — Impact test method and classification for flat glass*

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001. Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager. Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553. Email: copyright@bsi-global.com.